

11/21/2023



Producer: Kendall Portsmouth

Material: 4/10

Specific.: EN12620 4 / 10 GC85/20 f1,5


TestOrder No	Seq	Date	Specifica tion	Moisture Content	Flakines s Index	20	16	14	12.5	10	8	6.3	5	4	2.8	2	1	0.063
tKWA/0113626	6	07-Nov-23	OK	5.2		100	100	100	100	91	60	24	3	0	0	0	0	0
tKWA/0113240	4	31-Oct-23	OK	5.1	10	100	100	100	100	86	53	22	4	1	0	0	0	0
tKWA/0112956	3	23-Oct-23	OK	5.3		100	100	100	100	90	63	27	5	1	0	0	0	0
tKWA/0112436	2	16-Oct-23	OK	4.6		100	100	100	100	85	49	17	2	0	0	0	0	0.1
tKWA/0112098	1	10-Oct-23	OK	3.9		100	100	100	100	88	60	24	4	0	0	0	0	0
tKWA/0111918	5	05-Oct-23	OK	4.5		100	100	100	99	85	48	17	3	1	1	1	1	0



Producer: Kendall Portsmouth

Material: 4/10

Specific.: EN12620 4 / 10 GC85/20 f1,5

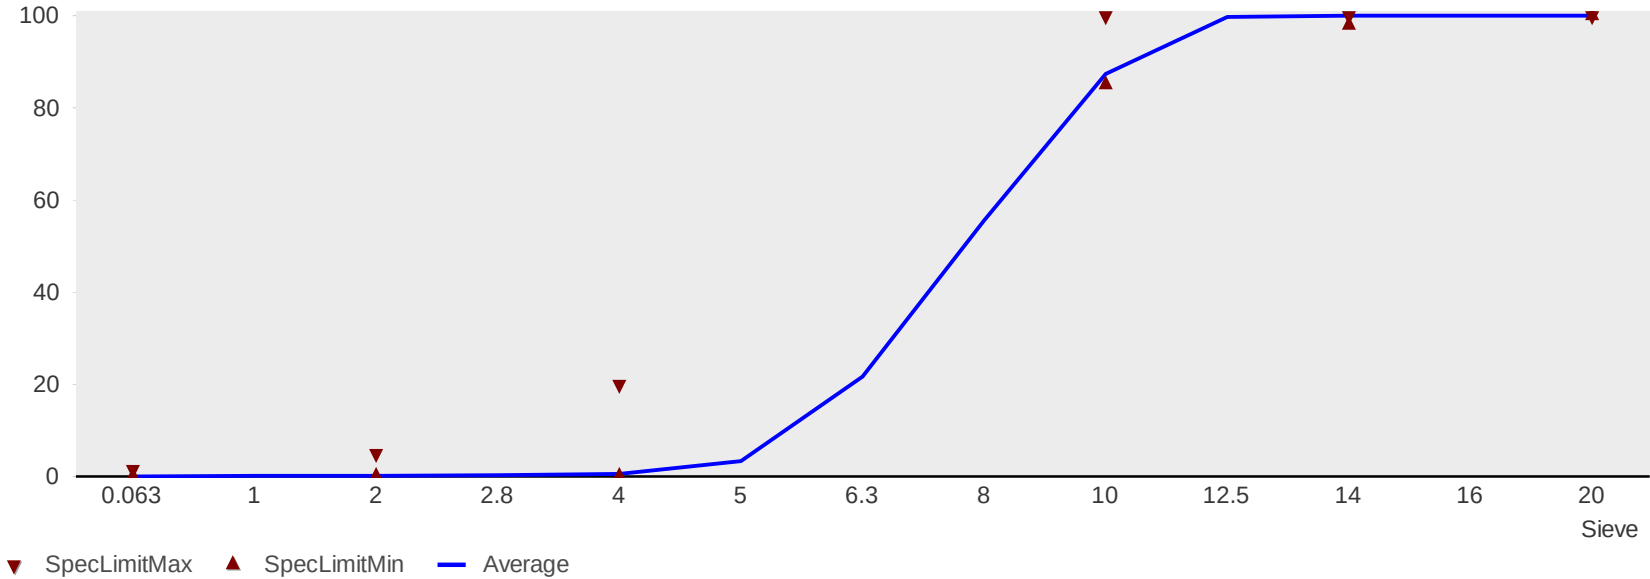

	Specif...	Moisture Content	Flakiness Index	20	16	14	12.5	10	8	6.3	5	4	2.8	2	1	0.063
Count	6	6	1	6	6	6	6	6	6	6	6	6	6	6	6	6
Average		4.8	10	100	100	100	100	87	56	22	3	1	0	0	0	0
Upper Specification Limit			50	100		100		100				20		5		1.5
Lower Specification Limit				100		98		85				0		0		0
Max Value		5.3	10	100	100	100	100	91	63	27	5	1	1	1	1	0.1
Min Value		3.9	10	100	100	100	99	85	48	17	2	0	0	0	0	0